



Designation: D953 – 19

Standard Test Method for Pin-Bearing Strength of Plastics¹

This standard is issued under the fixed designation D953; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ε) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the U.S. Department of Defense.

1. Scope*

1.1 This test method covers the determination of the pin-bearing strength of rigid plastics in either sheet form, molded form, or in reinforced thermoset form. Procedures A and B are applicable for thermoplastic materials in tension loading and compression loading respectively. Procedure C is applicable for thermoset reinforced plastics. See the significance and use section (Section 5) for cautions in using this test standard.

1.2 Test data obtained by this test method is relevant and appropriate for use in quality control and engineering design.

1.3 The values stated in SI units are to be regarded as the standard. The values given in parentheses are for information only.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

NOTE 1—This standard and ISO 12815 address the same subject matter, but differ in technical content.

1.5 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

2. Referenced Documents

2.1 ASTM Standards:²

D618 Practice for Conditioning Plastics for Testing
D883 Terminology Relating to Plastics

¹ This test method is under the jurisdiction of ASTM Committee D20 on Plastics and is the direct responsibility of Subcommittee D20.18 on Reinforced Thermosetting Plastics.

Current edition approved Nov. 1, 2019. Published December 2019. Originally approved in 1948. Last previous edition approved in 2018 as D953 - 18. DOI: 10.1520/D0953-19.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

D5947 Test Methods for Physical Dimensions of Solid Plastics Specimens

D7290 Practice for Evaluating Material Property Characteristic Values for Polymeric Composites for Civil Engineering Structural Applications

E4 Practices for Force Verification of Testing Machines

E177 Practice for Use of the Terms Precision and Bias in ASTM Test Methods

E6 Terminology Relating to Methods of Mechanical Testing

E691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method

2.2 ISO Standards:

ISO 12815 Fibre-reinforced plastic composites—Determination of plain-pin bearing strength³

3. Terminology

3.1 *Definitions*—For definitions of technical terms used in this test method and associated with plastics issues refer to terminology contained in ASTM D883.

3.2 Definitions of Terms Specific to This Standard:⁴

3.2.1 *pin-bearing area*—the diameter of the hole multiplied by the thickness of the specimen.

3.2.2 *pin-bearing strength*—the pin-bearing stress at which the pin-bearing hole is deformed 4 % of its diameter for thermoplastics. For thermosets, the pin-bearing strength is the maximum pin-bearing stress at which the sample fails.

3.2.3 *pin-bearing stress*—the applied load in newtons (or pounds-force) divided by the pin-bearing area in mm² (or in²).

3.2.4 *edge distance ratio*—the distance from the center of the pin-bearing hole to the edge of the specimen in the direction of loading, divided by the diameter of the hole.

3.2.5 *maximum pin-bearing stress*—the maximum load in newtons (or pounds-force) sustained by the specimen, divided by the bearing area.

4. Summary of Test Method

4.1 This test standard is intended to test the pin-bearing strength of thermoplastic material using procedures A, B and

³ Available from American National Standards Institute (ANSI), 25 W. 43rd St., 4th Floor, New York, NY 10036, <http://www.ansi.org>.

⁴ Attention is also directed to Terminology E6.

*A Summary of Changes section appears at the end of this standard

reinforced thermoset plastics using procedure C. In procedures A and B, the sample with a pin-bearing hole will be tested in tension and compression respectively. While using procedure A and B, the load at which the hole deformation reaches 4 % of hole diameter, that load shall be considered as maximum pin-bearing load to calculate the pin-bearing strength. In procedure C, the sample shall be tested in compression and the maximum failure load of the sample shall be used as maximum pin-bearing load to calculate the pin-bearing strength. As reinforced thermoset plastics are much stiffer than thermoplastics, the pin-bearing failure happens much before the hole deformation reaches 4 % of the hole diameter. Using procedure C, it is allowed to test reinforced thermoset samples with over-sized holes for any engineering design purposes. Using the maximum pin-bearing load obtained by using an appropriate procedure, the pin-bearing strength of the material will be determined.

5. Significance and Use

5.1 This pin-bearing strength test for plastics is intended to apply in the specification of various thermoplastic or thermosetting products in sheet form where rivets, bolts, or similar fastenings are to be used in joining members or sections. It also is intended to apply wherever sheet materials of the classes indicated are required to sustain edgewise loads that are applied by means of pins or rods of circular cross section which pierce the sheet perpendicular to the surface.

5.2 The purpose of the test using procedures A and B is to determine the pin-bearing strength of thermoplastic material and to plot the pin-bearing stress versus the deformation of the hole. The allowable deformation of the hole in the material shall be such as to produce no looseness of joints.

5.3 The purpose of procedure C is to determine the ultimate pin-bearing strength of reinforced thermoset material. This test procedure enables the user to test the part in any direction that is intended to carry the pin-bearing loads. The sample size used in this procedure will cover thermoset reinforced plastics that are commonly used in infrastructure applications.

5.4 While it is a known fact that higher strength materials will generally give higher bearing strengths, there is no satisfactory method to estimate pin-bearing strength from tensile or compressive properties of the material.

5.5 Before proceeding with this test method, reference shall be made to the specification of the material being tested. Any test specimen preparation, conditioning, dimensions or testing parameters or combination thereof covered in the relevant ASTM materials specification shall take precedence over those in this test method. If there are no relevant ASTM material specifications then the default conditions apply.

6. Apparatus

6.1 *Testing Machine*—A properly calibrated universal testing machine that is capable to be operated at a speed of 1.3 ± 0.3 mm (0.05 $\pm$ 0.01 in.)/min, except that in cases of certain types of materials where it is necessary to operate at a slower speed. The percentage of error of the testing machine shall be

no more than ± 1 % of the applied load as determined in accordance with Practices E4.


6.2 *Tension Loading Fixture for Procedure A*—A three-plate fixture of hardened steel similar to that shown in Fig. 1.

6.3 *Extension Indicator*—A suitable instrument reading in 0.0025 mm (0.0001 in.) for indicating the movement of the free end of the specimen with relation to the bearing pin in the tension loading fixture. A dial gauge fitted with accessories for this purpose is shown in Fig. 2.

6.4 *Compression Loading Fixture for Procedure B*—A type of support with a suitable bearing pin similar to Fig. 3.

6.5 *Compression Indicator*—A suitable instrument reading to 0.0025 mm (0.0001 in.) for indicating the movement of the free end of the specimen with relation to the bearing pin in the compression loading fixture. A schematic of the dial gauge assembly for this purpose is shown in Fig. 4.

6.6 *Compression Loading Fixture for Procedure C*—The fixture as shown in Fig. 5 (A) is made up of two properly aligned steel angle uprights welded to a steel base plate. The welding of the angle uprights has to be on the outside only and not for the surfaces against which the specimen makes contact

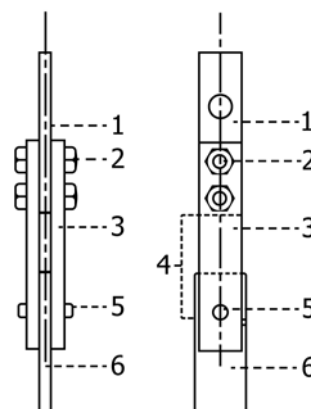

- 1—Hardened spacer plate.
- 2—6.3-mm (-in.) steel bolts in reamed holes.
- 3—Hardened side plate.
- 4—Extensometer span.
- 5—Hardened steel pin in reamed hole.
- 6—Test specimen.

NOTE 1—Critical dimensions are as follows:

Type	Bearing Hole Diameter, mm (in.)	Bearing Pin Diameter, mm (in.)	Thickness of Spacer Plate, mm ^A (in.)
I	3.175 + 0.025 – 0.000 (0.125 + 0.0010 – 0.0000)	3.150 + 0.000 – 0.025 (0.124 + 0.0000 – 0.0010)	3.2 (¹ / ₈)
II	6.350 + 0.025 – 0.000 (0.250 + 0.0010 – 0.0000)	6.325 + 0.000 – 0.025 (0.249 + 0.0000 – 0.0010)	6.3 (¹ / ₄)

^A The spacer plate shall be shimmed to a thickness of 0.025 to 0.125 mm (0.001 to 0.005 in.) greater than the specimen under test.

FIG. 1 Steel Tension Loading Fixture